

COMPARABLE STANDARD

Typical Analysis %	C	Si	Mn	P	S	Cr	Mo	Cu
Minimum					0.15	12.00		
Maximum	0.15	1.00	1.25	0.060		14.00	0.60	0.50

DESCRIPTION

Ugitech's 416 is a free machining martensitic grade. The unique production process—developed exclusively by Ugitech—results in a product that delivers superior productivity, tool life and consistency, and improves the surface finish on all types of machined parts. Machined parts are frequently used in the annealed condition, but may be heat-treated to develop optimum mechanical properties for specific applications.

416 HT, condition T (HRc 26-32), is the popular heat-treated version of **416**. This condition is specified for numerous engineering applications, and represents the optimum condition for both machinability and corrosion resistance. No further heat treatment of machined parts is required.

These grades deliver heat to heat consistency that is unsurpassed in the industry. Once an optimum set-up has been established, machinists can take advantage of increased machine efficiency rates (run “lights out production”). Also, crashes due to hard spots are a thing of the past. **416** and **416 HT** can both provide a significant competitive advantage for shops that demand efficient, high volume and reliable production.

CLASSIFICATION

Free Machining Martensitic stainless steel. Oxidation resistance in continuous service to 1200°F (650°C).

CHARACTERISTICS

- AISI Type 416
- UNS S41600
- ASTM A314
- ASTM A473
- ASTM A484
- ASTM A581-Chemistry
- ASTM A582
- ASTM F899

* Not applicable in all situations, must be requested at time of order placement.

- AMS 5610 Type 2
- QQ-S-763
- QQ-S-764
- SAE J405 No. 51416
- EN 10088-3
1.4401/1.4005
X12CrS13

AVAILABLE FORMS

Cold drawn bars, Turned bars, Ground bars, Wire, SMQ™

MECHANICAL PROPERTIES (TYPICAL)

Annealed Properties	
Cold Drawn Bars (1" and under)	
- Tensile Strength	90 - 120 ksi (620 - 830 MPa)
- Yield Strength (0.2)	80 - 105 ksi (550 - 725 MPa)
- Elongation	10% Minimum
- Reduction of Area	40% Minimum
- Hardness	190-240 BHN
Turned Bars (Over 1")	
- Tensile Strength	90 - 110 ksi (650 - 750 MPa)
- Yield Strength (0.2)	65 - 85 ksi (510 - 580 MPa)
- Elongation	20% Minimum
- Reduction of Area	60% Minimum
- Hardness	190 - 210 BHN
Heat Treat Properties (Condition T HRc 26–32)	
All Sizes	
- Tensile Strength	129 - 150 ksi (890 - 1035 MPa)
- Yield Strength (0.2)	110 - 130ksi (760 - 895 MPa)
- Elongation	5% Minimum
- Reduction of Area	40% Minimum
- Hardness	27-31 HRc (264-294 BHN)

MAGNETIC AND ELECTRICAL PROPERTIES

Typical Magnetic Permeability:

- Magnetic in all conditions.

Electrical Resistivity

- 22 $\mu\Omega$ - in (550 $\mu\Omega$ - mm) @ 68°F (20°C)

PHYSICAL PROPERTIES (TYPICAL)

Density	0.276 lbs/in ³ (7.6 g/cm ³)
Mean Coefficient of Linear Expansion	68-392 °F (20-200 °C) = 6.0×10^{-6} in/in/°F (10.8 x 10 ⁻⁶ cm/cm/°C)
Modulus of Elasticity in Tension	29.7×10^6 psi (205,000 MPa)
Thermal Conductivity	14.4 Btu/ft/hr/°F (25.1 W/m/°C) @68°F (20°C)

FORGING (HOT WORKING)

416 is not a forging grade, but can be forged if necessary. It is not recommended for upsetting operations. The following heating and handling conditions are recommended.

- Slow heating to 1475° F (800° C), then more rapidly to 2100-2150°F (1150-1180° C)
- Forge in the range of 1750-2150° F (950-1180°C)
- After forging, slow cooling in the furnace

CORROSION RESISTANCE

Ugitech's **416** in the annealed and heat treated conditions offer good corrosion resistance in moderately aggressive, non-chlorinated media (e.g. soaps, solvents, and organic acids), fresh water, steam, many petroleum products, and mold atmospheres. Care should be taken when specifying **416**, as with any sulfur bearing stainless steel, for use in environments that encourage localized attack such as pitting and crevice corrosion. Therefore, competent design should avoid areas that will allow corrosive products to collect and stagnate while in service. In general **416 HT**, **416** condition T (HRc 26-32) represents the optimum condition for corrosion resistance. Resistance to scaling for Ugitech's **416** is approximately 1200°F (650°C). This temperature can change depending upon the type of environment and application.

The corrosion resistance of a stainless steel depends on many factors related to the composition of the corrosive element, pH, temperature, velocity, agitation, services, deposits, dissimilar metal contact, metallurgical condition, as well as the preparation of the surface. The table here is for comparative purposes only and illustrates the performance in different environments. Consult your local **SWISS STEEL USA** metallurgist to discuss your application.

Optimum corrosion resistance requires that parts be smooth, and free from surface contamination such as cutting fluid and foreign particles. Under these conditions, parts will be passive in the air. Due to complexity and cost, passivation of **416** and **416 HT** should be avoided. However, if passivation is required, the following treatment is recommended (reference ASTM A380):

- Solution: 20–50% nitric acid + 2-6 wt. sodium dichromate at 70-120°F (20-50°C).
- Treatment: Immerse for 25-40 minutes followed by thorough rinsing to remove all residual solution

ENVIRONMENT	BEHAVIOR
Nitric Acid	○○○○ Restricted
Humidity	●●○○
Phosphoric Acid	○○○○ Restricted
NaCl (Saline Mist)	○○○○ Restricted
Sulfuric Acid	○○○○ Restricted
Seawater	○○○○ Restricted
Acetic Acid	○○○○ Restricted
Petroleum	○○○○ Restricted
Sodium Carbonate	●●○○

It is important to note, maintaining corrosion resistance at weld zones will require cleaning and passivation.

HARDENABILITY (COLD WORKING)

Hardenable by heat treatment. Strength and hardness increase slightly upon cold work such as drawing and forming.

HEAT TREATMENT

Annealing

- The heat treatment (annealing) that gives **416** its softest properties includes heating at 1650°F (900°C), followed by slow cooling in the furnace.

Sub-critical anneal

- Heat 1200°F to 1400°F (650°C to 760°C) followed by air cooling

Hardening

- Ugitech's **416** can be heat treated (hardened and tempered) to different hardness ranges for different applications. The hardening should be performed at 1750°F (950°C), followed by air or oil quenching. Oil quenching should be used on larger sections. Air quenching smaller sections can reduce quench hardness by one or two Rockwell points. Typical max. quench hardenability ranges from HRc 41 to HRc 43.

- The tempering temperatures should be selected depending on desired final properties required - see **416** hardenability chart below.

- Caution: Tempering of **416** in the range of 750-1110°F (400-600°C) results in reduced corrosion resistance and decreased impact strength. However, it may be necessary to temper in this range to obtain necessary strength levels. Care should be taken in the design of parts to compensate for these reduced properties.

- Contact your local **SWISS STEEL USA** application engineer with specific concerns.

Stress Relieving


Ugitech's **416** can be stress relieved as follows:

- Hardened and tempered - Heat and hold 50°F to 100°F (10°C to 40°C) below tempering temperature for 4-7 hours, slow cool.
- Annealed - Heat and hold 1100°F (595°C) for 4-7 hours, slow cool.

MACHINABILITY

The key to **416** lies in the production process. Careful control of alloy content and distribution of metallurgical phases results in better tool life, improved surface finish, and excellent chip control across a wide range of cutting conditions. **416 HT** represents the optimum condition for machinability.

The table on the following page, in conjunction with the recommendations below it, provides a useful guideline for initial set-up. To realize the optimal potential of either grade, contact your local application engineer. A review of your current set-up will allow specific recommendations adapted to **416** or **416 HT**.

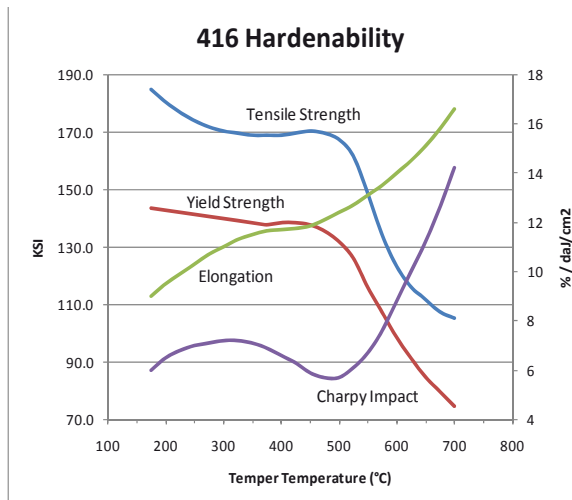

WELDING

Similar to any sulfur bearing stainless steel, the welding of **416** should be avoided since the high sulfur content can result in cracking. This is particularly true for welding processes where no filler metal is used (except for friction welding). If welding is required, AWS E309/ER309 is recommended as filler metal. A tempering heat treatment at 1200° F (650° C) after welding may be useful in restoring ductility to the welded area. Gas welding with hydrogen or nitrogen gas should be avoided.

		HSS TOOLING			COATED CARBIDE TOOLS			
Machining Operations	Metallurgical Condition	Depth of cut or width (in.)	Cutting Speed SFPM	Feed (ipr)	Type of Tool	Cutting Speed SFPM	Feed (ipr)	Type of Tool
Turning	Cold Drawn	0.04	120-160	0.003-0.008	M2-M3 (T15)	460-900	0.005-0.008	C7
		0.08	100-140	0.003-0.010		425-800	0.006-0.010	C6
		0.12	80-130	0.004-0.012		375-700	0.006-0.012	C6
	Annealed	0.04	130-170	0.003-0.008	M2-M3 (T15)	505-950	0.005-0.008	C7
		0.08	110-150	0.003-0.010		375-850	0.006-0.010	C6
		0.12	90-140	0.004-0.012		325-750	0.006-0.012	C6
Forming & Grooving	Cold Drawn	0.08	110-150	0.001-0.003	M2-M3 (T15)	360-500	0.002-0.003	C6
		0.25	100-140	0.003-0.005		295-400	0.003-0.004	C6
		0.50	90-140	0.002-0.004		210-350	0.003-0.004	C6
		1.00	70-110	0.002-0.003		175-300	0.002-0.003	C6
		2.00	60-100	0.002-0.003		150-200	0.002-0.003	C6
	Annealed	0.08	120-160	0.002-0.004	M2-M3 (T15)	390-550	0.002-0.004	C6
		0.25	110-150	0.003-0.005		325-450	0.002-0.004	C6
		0.50	100-150	0.002-0.005		245-400	0.002-0.004	C6
		1.00	80-120	0.002-0.004		200-330	0.002-0.003	C6
		2.00	70-110	0.002-0.003		185-250	0.002-0.003	C6
Shaving & Skiving	Cold Drawn	0.08	120-150	0.001-0.003	M2-M3 (T15)	360-500	0.002-0.003	C6
		0.25	110-140	0.001-0.0025		295-400	0.003-0.004	C6
		0.50	100-140	0.001-0.002		210-350	0.002-0.004	C6
		1.00	80-110	0.001-0.002		175-300	0.002-0.003	C6
		2.00	70-100	0.001-0.002		150-200	0.002-0.003	C6
	Annealed	0.08	130-160	0.001-0.003	M2-M3 (T15)	390-550	0.002-0.004	C6
		0.25	120-150	0.001-0.0025		325-450	0.002-0.004	C6
		0.50	110-150	0.001-0.002		245-400	0.002-0.004	C6
		1.00	90-120	0.001-0.002		200-330	0.002-0.003	C6
		2.00	80-110	0.001-0.002		185-250	0.002-0.003	C6
Cut-Off or Part-Off	Cold Drawn	0.04	80-120	0.001-0.002	M41 (T15)	295-575	0.002-0.003	C6
		0.08	70-110	0.001-0.0025		320-530	0.002-0.003	C6
		0.12	60-100	0.0015-0.003		320-500	0.002-0.003	C6
	Annealed	0.04	80-130	0.001-0.0025	M41 (T15)	325-600	0.002-0.003	C6
		0.12	70-120	0.0015-0.003		300-575	0.002-0.003	C6
		0.25	60-110	0.002-0.004		300-550	0.003-0.004	C6

Machining Operations	Metallurgical Condition	Depth of cut or width (in.)	HSS TOOLING			COATED CARBIDE TOOLS		
			Cutting Speed SFPM	Feed (ipr)	Type of Tool	Cutting Speed SFPM	Feed (ipr)	Type of Tool
Drilling	All	0.063	30-115	0.005-0.002	M2	50-250	0.0005-0.002	C5-C6 or C1-C2 TiN Coated
		0.125		0.002-0.004			0.002-0.004	
		0.250		0.003-0.006			0.002-0.005	
		0.500		0.005-0.009			0.004-0.006	
		0.750		0.008-0.012			0.006-0.009	
Insert Drilling	All	0.50-0.75				150-400	0.001-0.004	C7
		0.75-1.00				200-500	0.002-0.005	C6
		1.00-2.50				250-600	0.002-0.006	C5
Reaming	All	0.062	30-115	0.002-0.005	M2 (M42)	50-250	0.002-0.005	C5-C or C3 TiN Coated
		0.125		0.004-0.008			0.004-0.008	
		0.250		0.007-0.016			0.007-0.016	
		0.500		0.015-0.025			0.015-0.025	
		0.750		0.015-0.030			0.015-0.030	
1.000	0.020-0.030	0.020-0.030						
Tapping	All	All	20-80		M2-M7 TiN Coated			

The machining data presented within all tables and graphs represent typical working ranges based on field and laboratory research. Results will vary based on parts to be produced, equipment and tooling utilized, personnel operating the equipment and customer part specifications. For additional information, contact Technical Support at the Corporate Office: (800) 323-1233.

MACHINABILITY TABLE GUIDELINES

- For heat treated **416 HT**, the following adjustments should be made to the standard annealed condition as presented in the **416** Machinability Table:
 - On all operations except drilling, speed should be decreased 20% with HSS tooling and increased 20% when using Carbide tooling.
 - Carbide grade ANSI C6 or better is the best all-purpose choice of carbide grades for machining **416 HT**.

- For drilling, speeds and feeds should remain the same as **416**.
- Feed rates in all cases should remain the same as **416**.

- Grades of tooling in parenthesis indicate an alternate or second choice of tooling.
- When using the C1-C4 grade carbides, decrease speed by 25-40%.
- When using coated tools, speeds and feeds should be increased by 10-15%.
- Drill speeds were developed for 118° drills. Increase speeds 10-20% with use of 130° to 140° angle drills.
- For drilling deeper than 3x diameter, reduce speed and feed by 20-40% for straight drilling, or set decreasing pecking depth to 2x diameter max.

NORTH AMERICAN DISTRIBUTION

HEADQUARTERS +
TECHNICAL SUPPORT

SWISS STEEL USA, INC.
365 Village Dr.
Carol Stream, IL 60188
Phone: 800.323.1233
Fax: 630.879.0498

MANUFACTURING +
CENTRAL STOCKING FACILITY

SWISS STEEL USA, INC.
1609 E. Wilson Street
Batavia, IL 60510

DISTRIBUTION LOCATIONS

WEST COAST

556 Vanguard Way
Brea, CA 92861

MIDWEST

365 Village Dr.
Carol Stream, IL 60188

1455 Miller Pkwy.
Streetsboro, OH 44241

SOUTHEAST

119 Old Airport Rd.
Roebuck, SC 29376

NORTHEAST

370 Franklin Turnpike
Mahwah, NJ 07430

CANADA

SWISS STEEL CANADA, INC.
6350 Vipond Dr.
Mississauga, ONT L5T 1G2

www.swisssteel-international.us
www.swisssteel-international.ca

LEGAL NOTICE All statements regarding the properties or utilization of the materials or products mentioned are for the purposes of description only. Guarantees regarding the existence of certain properties or a certain utilization are only valid if agreed upon in writing.

